

## Crystal fields and the $\gamma \rightarrow \alpha$ transition in Ce

Sukalpa Basu, Peter S. Riseborough\*

*Department of Physics, Temple University, Philadelphia, USA*

### Abstract

In the  $\gamma \rightarrow \alpha$  transition of Ce, the material undergoes an isostructural change at which the volume changes by 15% and the magnetic character changes. Recently, the transition has been described in terms of a balance between the free-energy of the magnetic moments and the characteristic energy scale of the  $\alpha$  phase. The field-temperature dependence of the phase diagram has been predicted, and was confirmed by experiment. Inelastic neutron scattering experiments on the  $\gamma$  phase of Ce have shown indications of crystal field splittings, and similar experiments have determined the energy scale of the  $\alpha$  phase. We shall examine the effects of the crystalline field splittings within the framework of NCA calculations on the single-impurity Anderson model, and examine their consequence for the phase diagram.

© 2006 Elsevier B.V. All rights reserved.

PACS: 71.10.Hf; 71.27.+a; 75.30.Mb

Keywords:  $\alpha \rightarrow \gamma$  Phases of Ce; Crystal field levels

The  $\gamma \rightarrow \alpha$  transition in Ce has been the subject of much investigation since the 1940s. The transition between the high-temperature  $\gamma$  phase and the low-temperature  $\alpha$  phase is isostructural and is manifested by a large decrease in volume ( $\sim 17\%$ ) [1]. In the high-temperature  $\gamma$  phase, the magnetic susceptibility follows a Curie–Weiss temperature dependence, but in the low-temperature  $\alpha$  phase, the susceptibility is suppressed and follows a Pauli–paramagnetic temperature dependence, with a characteristic energy which was later found to be as large as 165 meV [2]. Pauling [3] and Zachariassen suggested that the f electrons are squeezed into the valence band in the transition. The Pauling–Zachariassen model was challenged when Gustafson and co-workers [4] performed positron annihilation measurements which indicated that there was no significant change in the number of f electrons. Subsequently, Johansson [5] suggested that the transition was a Mott transition in which the localized magnetic 4f electron states were transformed into a broad non-magnetic 4f band of Bloch states. However, photoemission experiments contradict a simplified picture of the Mott transition. Allen and

Martin then suggested that the phase transition was due to a Kondo volume collapse [6]. In this picture, the transition is due to the competition between the entropy of the six-fold degenerate magnetic ion in the high-temperature state and the binding energy of a Kondo singlet ( $\sim k_B T_K$ ) formed in the low-temperature state. This requires that the electronic entropy change, per Ce ion, should be of the order of  $k_B \ln 6 \sim 1.79 k_B$ , which is similar to the total entropy change of  $1.54 k_B$  inferred from the latent heat. However, at high pressure, measurements of the Debye–Waller factor indicate that roughly  $0.75 k_B$  of the total entropy change is associated with phonons [7]. These measurements and the results of our present NCA calculations, which yield an electronic entropy change of only about  $1.1 k_B$ , suggest that the lattice must play an important role in the transition. In fact, the lattice energy, along with the local correlation energy, has been calculated within the local-density-functional dynamical-meanfield approximation [8]. These calculations are promising as they show features consistent with the existence of the observed critical end-point at  $T_c \sim 550$  K.

We shall compare our NCA calculations including cubic crystal field splittings with the neutron scattering data on the  $\gamma$  phase at ambient pressures [9,10] and we shall also

\*Corresponding author. Tel.: +1 215 204 5655; fax: +1 215 204 5652.

E-mail address: [sukalpa.basu@temple.edu](mailto:sukalpa.basu@temple.edu) (S. Basu).

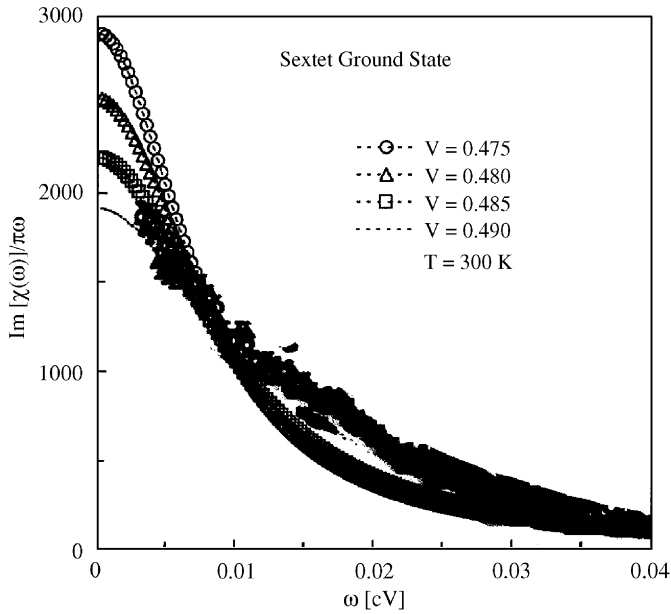


Fig. 1. A comparison of the NCA calculations with  $J = \frac{5}{2}$  and no crystal field splittings and various values of the hybridization  $V$  (in eV), with the experimental data of McQueeney et al. [9].

with the experimentally determined phase diagram of  $\text{Ce}_{0.8}\text{La}_{0.1}\text{Th}_{0.1}$  [11].

We have calculated the neutron scattering cross-section of the single impurity Anderson model using the NCA, with  $J = \frac{5}{2}$  (Fig. 1). The best fit of the neutron scattering on  $\gamma$  Ce shows evidence of a broadened crystal field level at about 18 meV. Due to the large width of the inelastic “peak” [10], comparison of the data with calculations assuming a cubic crystal field is indecisive as to whether the crystal field quartet or the doublet has the lowest energy. The quartet ground state does produce a slightly better fit. The calculated value of the  $f$  occupation is about 0.95 for the  $\gamma$  phase and is 0.8 in the  $\alpha$  phase. The value of 0.8 is consistent with a Kondo condensation energy of 165 meV [2]. Since the  $\gamma$  phase is dominated by the local moments which are absent in the  $\alpha$  phase, Dzero et al. suggested that the  $(B, T)$  phase diagram should be determined by the balance of the magnetic free energy with the (field-independent) condensation of the low-temperature phase [12]. In Fig. 2, we show the effects of crystal field splitting on the observed phase diagram of  $\text{Ce}_{0.8}\text{La}_{0.1}\text{Th}_{0.1}$  [11]. It is seen that the experimental data support the hypothesis of a crystal field doublet ground state. Since this is also inconclusive, we suggest that the observation of a metamagnetic transition for fields of the order of 200 T would conclusively demonstrate that the doublet is the crystal field ground state. The metamagnetic transition is predicted to be absent for a quartet crystal field ground state.

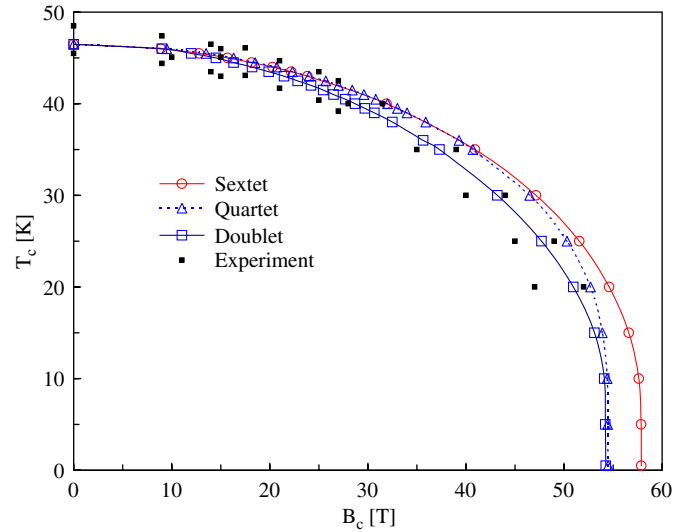


Fig. 2. The calculated phase diagram of  $\text{Ce}_{0.8}\text{La}_{0.1}\text{Th}_{0.1}$  assuming cubic crystal fields with a splitting of 18 meV, no crystal field splitting and the experimental data (filled squares) [11].

We have analyzed the results of inelastic neutron scattering in the  $\gamma$  phase of Ce and find evidence of (broadened) crystal field splittings. Support for the existence of these crystal field levels is provided by analysis of the phase diagram of  $\text{Ce}_{0.8}\text{La}_{0.1}\text{Th}_{0.1}$ . A definitive determination of the crystal field ground state may be provided by the observation of a metamagnetic transition at high fields. Our NCA calculations, with crystal field splittings, do show that a significant fraction of the entropy change in the  $\gamma \rightarrow \alpha$  transition is of non-electronic origin. Therefore, we conclude that the lattice does play an important role in the transition.

## References

- [1] A.W. Lawson, T.Y. Tang, *Phys. Rev.* 76 (1949) 301.
- [2] A.P. Murani, Z.A. Bowden, A.D. Taylor, R. Osborn, W.G. Marshall, *Phys. Rev. B* 48 (1983) 13981.
- [3] L. Pauling, *J. Am. Chem. Soc.* 69 (1947) 542.
- [4] D.R. Gustafson, et al., *Phys. Rev.* 183 (1969) 435.
- [5] B. Johansson, *Phil. Mag.* 30 (1974) 469.
- [6] J.W. Allen, R.M. Martin, *Phys. Rev. Lett.* 74 (1982) 1006.
- [7] I.-K. Jeong, T.W. Darling, M.J. Graf, Th. Proffen, R.H. Heffner, Y. Lee, T. Vogt, J.D. Jorgensen, *Phys. Rev. Lett.* 92 (2004) 105702.
- [8] K. Held, A.K. McMahan, R.T. Scalettar, *Phys. Rev. Lett.* 87 (2001) 276404.
- [9] R.J. McQueeney, M.E. Manley, R. Osborn, B. Fultz, G.H. Kwei, P.D. Bogdanoff, *Philos. Mag. B* 81 (2001) 675.
- [10] B.D. Rainford, B. Buras, B. Lebech, *Physica B* 86–88 (1977) 41.
- [11] F. Drymiotis, J. Singleton, N. Harrison, J.V. Lashley, A. Bangura, C.H. Mielke, L. Balicas, Z. Fisk, A. Migliori, J.L. Smith, *J. Phys.: Condens. Matter* 17 (2005) L77.
- [12] M.O. Dzero, L.P. Gor'kov, A.K. Zvezdin, *J. Phys.: Condens. Matter* 12 (2000) L711.